


DR 91131

AS 2835.2—1985
UDC 615.468.2

Australian Standard[®] 2835.2—1985

PPB ED.

ABSORBENT WOVEN GAUZE Part 2—COTTON-VISCOSE BLENDS

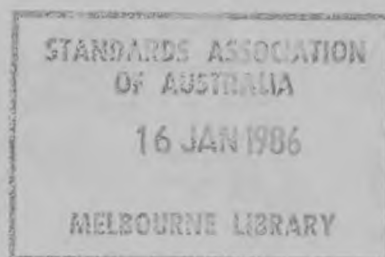

[Title Allocated by Defence Cataloguing Authority:
GAUZE, ABSORBENT (Cotton-viscose)]



STANDARDS ASSOCIATION OF AUSTRALIA
Incorporated by Royal Charter

This Australian standard was prepared by Committee MS/5, Institutional Supplies. It was approved on behalf of the Council of the Standards Association of Australia on 22 October 1985 and published on 2 December 1985.

The following interests are represented on Committee MS/5:

Australian Confederation of Operating Room Nurses

Australian Hospital Association

Australian Medical Association

AWTA Textile Testing

Confederation of Australian Industry

Department of Health, Commonwealth

Department of Health, N.S.W.

Department of Health, Qld.

Government Supply Department, N.S.W.

Health Commission of Victoria

Health Department of Western Australia

Royal Australasian College of Surgeons

Royal Australian Nursing Federation

Review of Australian Standards. To keep abreast of progress in industry, Australian standards are subject to periodic review and are kept up-to-date by the issue of amendments or new editions as necessary. It is important therefore that standards users ensure that they are in possession of the latest edition, and any amendments thereto.

Full details of all SAA publications will be found in the Catalogue of SAA Publications; this information is supplemented each month by SAA's journal 'The Australian Standard', which subscribing members receive, and which gives details of new publications, new editions and amendments, and of withdrawn standards.

Suggestions for improvements to Australian standards, addressed to the head office of the Association, are welcomed. Notification of any inaccuracy or ambiguity found in an Australian standard should be made without delay in order that the matter may be investigated and appropriate action taken.

This standard was issued in draft form for comment as DR 83256.

AUSTRALIAN STANDARD

ABSORBENT WOVEN GAUZE
Part 2
COTTON-VISCOSE BLENDS

AS 2835.2—1985

First published (as Commercial Standard 10, Part 2, Section 2)	1936
Revised	1941
Withdrawn	1979
Reinstated	1980
AS 2835.2 first published	1985

**PUBLISHED BY THE STANDARDS ASSOCIATION OF AUSTRALIA
STANDARDS HOUSE, 80 ARTHUR ST, NORTH SYDNEY, N.S.W.**

ISBN 0 7262 3982 8

PREFACE

This standard was prepared by the Association's Committee on Institutional Supplies to supersede Commercial Standard 10, Part 2, Section 2, Equipment and Supplies for Use in Public Institutions—Surgical Dressings—Unmedicated Gauze, 1936.

The standard specifies requirements for absorbent woven cotton-viscose gauze suitable for use in the manufacture of surgical dressings. Requirements for cotton gauze are specified in AS 2835.1.

Standards for surgical dressings manufactured from gauze complying with this standard or with AS 2835.1, are in the course of preparation.

In the preparation of this standard, consideration was given to the respective requirements of the British Pharmaceutical Codex 1973, the British Pharmacopoeia 1980 ('BP'), the European Pharmacopoeia (Vol. II) ('Eur. Ph.') and the United States Pharmacopoeia (Vol. XX) ('USP'). However, differences do occur between requirements set out in those publications and in this standard.

© Copyright — STANDARDS ASSOCIATION OF AUSTRALIA 1985

Users of standards are reminded that copyright subsists in all SAA publications. No part of this publication may be reproduced, stored in a retrieval system in any form or transmitted by any means without prior permission in writing of the Standards Association of Australia.

CONTENTS

	<i>Page</i>
SECTION 1. SCOPE AND GENERAL	
1.1 Scope	4
1.2 Referenced Documents	4
1.3 Classification	4
1.4 Definitions	5
1.5 Materials of Construction	5
SECTION 2. REQUIREMENTS	
2.1 General	6
2.2 Identification of Fibrous Components	6
2.3 Sinking Time	6
2.4 pH of Aqueous Extract	6
2.5 Level of Surface-active Substances	6
2.6 Content of Water-soluble Substances	6
2.7 Presence of Starch and Dextrins	6
2.8 Content of Ether-soluble Substances	6
2.9 Presence of Fluorescing Substances	6
2.10 Sulphated Ash Content	6
2.11 Colourfastness of Green Cotton-viscose Gauze	6
2.12 Viscose Content	6
2.13 Packaging	6
2.14 Marking	6

STANDARDS ASSOCIATION OF AUSTRALIA

Australian Standard
for
ABSORBENT WOVEN GAUZE

PART 2—COTTON-VISCOSE BLENDS

SECTION 1. SCOPE AND GENERAL

1.1 SCOPE. This standard specifies requirements for absorbent woven gauze comprised of a blend of cotton and up to 53 percent viscose, suitable for use in the manufacture of surgical dressings.

1.2 REFERENCED DOCUMENTS. The following standards are referred to in this standard:

- AS 2001 Methods of Test for Textiles
- 2001.2.3 Physical Tests—Determination of Breaking Force and Extension of Textile Fabrics
- 2001.2.5 Physical Tests—Determination of the Number of Threads per Unit Length in Woven Fabric
- 2001.3.1 Chemical Tests—Determination of pH of Aqueous Extract
- 2001.3.4 Part 3—Chemical Tests—Determination of Solvent-soluble Matter
- 2001.4.8 Colourfastness Tests—Determination of Colourfastness to Water
- 2001.7.2 Quantitative Analysis of Fibre Mixtures—General Requirements.
- 2001.7.6 Quantitative Analysis of Fibre Mixtures—Binary Mixtures of Viscose, Cupro or Certain Types of Polynosic (modal) and Cotton Fibres (method using formic acid and zinc chloride).

- AS 2836 Methods of Testing Surgical Dressings and Surgical Dressing Materials
- 2836.2 Method for the Identification of Cotton and Viscose Fibres
- 2836.3 Method for the Determination of Mass per Unit Area
- 2836.5 Method for the Determination of Sinking Time
- 2836.7 Method for the Determination of Level of Surface-active Substances
- 2836.8 Method for the Determination of Quantity of Water-soluble Substances
- 2836.9 Method for the Determination of the Presence of Starch and Dextrins
- 2836.10 Method for the Determination of the Presence of Fluorescing Substances
- 2836.11 Method for the Determination of Sulphated Ash Content

1.3 CLASSIFICATION. Absorbent woven cotton-viscose gauze shall be classified as one of the Grades specified in Table 1.1.

Where gauze is classified as a particular Grade, it shall comply with all requirements specified in Table 1.1 for that Grade and shall not comply with all requirements of any higher Grade.

NOTE: For the purposes of this Clause, A is regarded as the lowest and J as the highest grade of gauze.

TABLE 1.1
CLASSIFICATION OF COTTON-VISCOSE GAUZE

Grade (See Note)	Warp threads per centimetre, minimum mean	Weft threads per centimetre, minimum mean	Warp breaking force, minimum mean (N/50 mm)	Weft breaking force, minimum mean (N/50 mm)	Mass per unit area, minimum g/m ²
A	4.7	3.1	35	20	13.8
B	6.9	5.3	35	20	14.0
C	6.6	5.6	35	20	17.0
D	7.1	3.1	40	25	20.0
E	9.5	6.6	50	30	23.0
F	9.5	7.5	50	30	24.0
G	11.4	7.5	60	35	27.0
H	11.4	9.5	60	40	30.0
I	11.4	11.4	60	50	32.0
J	13.4	9.5	70	40	32.0

NOTE: Grades A to J correspond to the minimum requirements of USP Type VIII, BP Type 13 Light, Eur. Ph. Type 13 Heavy, USP Type VII, Eur. Ph. Types 17, 18, 20, 22, 24a and 24b respectively.