

Australian Standard[®]

**Electroplated coatings of zinc on steel
fasteners with imperial threads**

STANDARDS
Australia



This Australian Standard® was prepared by Committee MT-009, Metal Finishing. It was approved on behalf of the Council of Standards Australia on 6 February 2007. This Standard was published on 8 March 2007.

The following are represented on Committee MT-009:

- Australian Institute of Metal Finishing
 - Australian Chamber of Commerce and Industry
 - Australian Industry Group
 - Department of Defence
 - Galvanizers Association of Australia
 - The Royal Australian Chemical Institute
 - Society of Automotive Engineers, Australia
-

This Standard was issued in draft form for comment as DR 06594.

Standards Australia wishes to acknowledge the participation of the expert individuals that contributed to the development of this Standard through their representation on the Committee and through public comment period.

Keeping Standards up-to-date

Australian Standards® are living documents that reflect progress in science, technology and systems. To maintain their currency, all Standards are periodically reviewed, and new editions are published. Between editions, amendments may be issued.

Standards may also be withdrawn. It is important that readers assure themselves they are using a current Standard, which should include any amendments that may have been published since the Standard was published.

Detailed information about Australian Standards, drafts, amendments and new projects can be found by visiting **www.standards.org.au**

Standards Australia welcomes suggestions for improvements, and encourages readers to notify us immediately of any apparent inaccuracies or ambiguities. Contact us via email at **mail@standards.org.au**, or write to Standards Australia, GPO Box 476, Sydney, NSW 2001.

STANDARDS AUSTRALIA

RECONFIRMATION

OF

AS 4397—2007

Electroplated coatings of zinc on steel fasteners with imperial threads

RECONFIRMATION NOTICE

Technical Committee MT-009 has reviewed the content of this publication and in accordance with Standards Australia procedures for reconfirmation, it has been determined that the publication is still valid and does not require change.

Certain documents referenced in the publication may have been amended since the original date of publication. Users are advised to ensure that they are using the latest versions of such documents as appropriate, unless advised otherwise in this Reconfirmation Notice.

Approved for reconfirmation in accordance with Standards Australia procedures for reconfirmation on 20 March 2017.

The following are represented on Technical Committee MT-009:

Australasian Institute of Surface Finishing
Australian Chamber of Commerce and Industry
Australian Industry Group
Australian Steel Institute
Bureau of Steel Manufacturers of Australia
Galvanizers Association of Australia
Galvanizing Association of New Zealand
New Zealand Metal Roofing Manufacturers

NOTES

Australian Standard[®]

**Electroplated coatings of zinc on steel
fasteners with imperial threads**

Originated as AS K132.2—1963.
Previous edition AS 4397—1996.
Second edition 2007.

COPYRIGHT

© Standards Australia

All rights are reserved. No part of this work may be reproduced or copied in any form or by any means, electronic or mechanical, including photocopying, without the written permission of the publisher.

Published by Standards Australia, GPO Box 476, Sydney, NSW 2001, Australia

ISBN 0 7337 8099 7

PREFACE

This Standard was prepared by the Australian members of the Joint Standards Australia/Standards New Zealand Committee MT-009, Metal Finishing, to supersede AS 4397—1996, *Electroplated coatings of zinc on steel fasteners with imperial threads*. After consultation with stakeholders in both countries, Standards Australia and Standards New Zealand decided to develop this Standard as an Australian Standard rather than an Australian/New Zealand Standard.

The objective of this Standard is to specify requirements for zinc coatings on components with imperial threads for sectors of industry that have not converted to using metric threaded components.

The objective of this edition is to revise the zinc coating specifications and the means for complying with the Standard.

The terms ‘normative’ and ‘informative’ have been used in this Standard to define the application of the appendix to which they apply. A ‘normative’ appendix is an integral part of a Standard, whereas an ‘informative’ appendix is only for information and guidance.

CONTENTS

	<i>Page</i>
FOREWORD.....	4
1 SCOPE.....	6
2 REFERENCED DOCUMENTS.....	6
3 DEFINITIONS.....	7
4 DIMENSIONAL REQUIREMENTS BEFORE PLATING.....	7
5 COATING REQUIREMENTS	7
6 APPLICABILITY OF COATING TO STANDARD THREADS	9
7 APPLICABILITY OF COATING TO MODIFIED THREADS.....	9
8 HEAT TREATMENT OF STEEL FOR RELIEF OF STRESS AND HYDROGEN EMBRITTEMENT	10
9 CHROMATE CONVERSION COATINGS.....	10
APPENDICES	
A PURCHASING GUIDELINES.....	11
B MEANS FOR DEMONSTRATING COMPLIANCE WITH THIS STANDARD	12
C RECOMMENDED SAMPLING PLAN FOR THE INSPECTION OF COATINGS ON THREADED ITEMS.....	14
D PRETREATMENT OF IRON OR STEEL TO REDUCE THE RISK OF HYDROGEN EMBRITTEMENT	15
E POST-COATING TREATMENTS OF IRON OR STEEL TO REDUCE THE RISK OF HYDROGEN EMBRITTEMENT.....	18
F NOTES ON SURFACE AREAS OF IMPERIAL SCREWS, BOLTS AND NUTS...	22
G SPECIAL FACTORS FOR THE ELECTROPLATING OF SCREW THREADS	29
H EXAMPLES OF CALCULATIONS OF PLATING THICKNESSES	31
I EXAMPLES OF ‘NORMAL’ AND ‘THICKER’ PLATING	32
J EFFECT OF MANUFACTURING TOLERANCES ON PLATING THICKNESS CALCULATIONS FOR IMPERIAL THREADS	34
K EXAMPLE OF CALCULATION OF EXTERNAL THREAD DIMENSIONS TO ACCOMMODATE A THICKER COATING.....	36

FOREWORD

The Standard specifies the electrodeposition of zinc on threaded steel components. The nature of threaded items presents a number of problems which necessitate special care in the specification, application and inspection of electrodeposited coatings. Factors to consider include the following:

- (a) The thickness of an electrodeposit on parallel screw threads must be sufficient to provide the required resistance to corrosion but be not so great as to prevent assembly. Specifications for the electroplating of threaded items, therefore, are required to have both a maximum and a minimum value for the coating thickness.
- (b) Because of the geometry of screw threads, the theoretical change in pitch diameter caused by a plated deposit is several times the coating thickness. This change in pitch diameter depends on flank angles. In practice, it is generally greater than the theoretical value because of the tendency for the coating to be thicker on the crests of the threads resulting in a change of thread flank angle.

Figure 1 diagrammatically shows a coating which has been plated on an external screw thread; t is the thickness of coating, and θ is the angle between flanks of the thread. A coating thickness t on the external thread results in an increase in pitch diameter of $2t \operatorname{cosec} \theta/2$, which for a thread of included angle of 60 degrees increases the pitch diameter by an amount equal to $4t$.

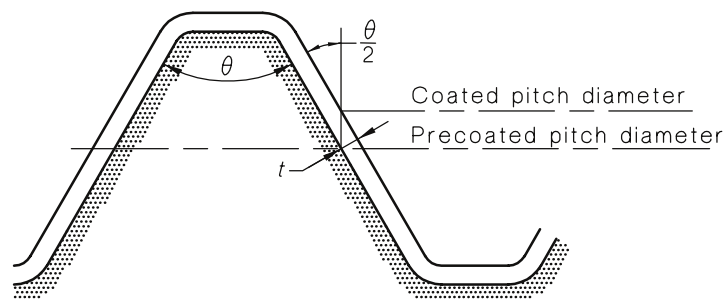


FIGURE 1 THEORETICAL CHANGE IN PITCH DIAMETER RESULTING FROM DEPOSIT OF THICKNESS (t)

- (c) With any form of electroplating, the coating tends to be preferentially deposited on projections and to be much thinner in any recess. For screws and bolts, the coating is thicker on the extremities and on the threaded ends of the items than on the centre of the bolt length. The longer the bolt in proportion to its diameter, the greater is this tendency. Fortunately, these extremities are the positions which are most significant in the ultimate service of the screw or bolt. Similarly for nuts, the thickness of coating on the threads is very much greater at the ends than on the interior threads. The greatest thickness will be on the outer surfaces which are most significant in service. In practice, thin coatings on the interior threads do not normally cause serious problems if sacrificial coatings are used, because they are normally in contact with the thicker coating on the external threads of the mating fastener. Furthermore, some slight variation in coating distribution occurs on the individual thread flanks, the tendency being for heavier deposition of coating at the crest of the thread than at the root. The effect of these variations is to increase the pitch diameter more than the theoretical value (see Item (b)). The clearance between an external and an internal thread is diagrammatically shown in Figure 2.