

DR. 91248

AS 1038.22—1983
UDC [662.66 + 662.74]:543.84:543.812/.81


1992 ED.

Australian Standard 1038.22—1983

AS 1038 Coal and coke—Analysis and testing
1038.22—1992 Higher rank coal—Mineral matter and water of constitution
(In Professional Package 32) 12pp E
Sets out two methods for the determination of mineral matter in coal, and a method for determination of water of constitution.
Committee MN/1: Supersedes AS 1038.22—1983: Draft for Comment
DR 91248: Publication date 1992-10-12: ISBN 0 7262 7665 0.

METHODS FOR THE ANALYSIS AND TESTING OF COAL AND COKE

Part 22—DIRECT DETERMINATION OF MINERAL MATTER AND WATER OF HYDRATION OF MINERALS IN HARD COAL

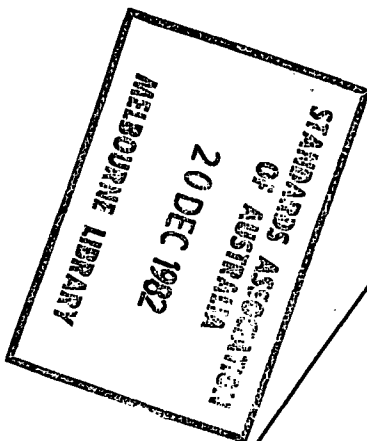

PUBLISHED BY THE STANDARDS ASSOCIATION OF AUSTRALIA
STANDARDS HOUSE, 80 ARTHUR ST, NORTH SYDNEY, N.S.W.

Incorporated by Royal Charter

This Australian standard was prepared by Committee MN/1, Coal and Coke. It was approved on behalf of the Council of the Standards Association of Australia on 21 September 1982 and published on 10 January 1983.

Represented on the committee which was responsible for the preparation of this standard were the following:

Australian Coal Association
Australian Institute of Energy
Australasian Institute of Mining and Metallurgy
Bureau of Steel Manufacturers of Australia
Coal Preparation Societies of N.S.W. and Queensland
Confederation of Australian Industry
CSIRO, Division of Fossil Fuels
Department of Minerals and Energy, Victoria
Department of Mineral Resources, N.S.W.
Department of National Development and Energy
Electricity Supply Association of Australia
Institution of Engineers, Australia
Joint Coal Board
Queensland Coal Board
Royal Australian Chemical Institute
Standing Committee on Coalfield Geology, N.S.W.
Universities

To keep abreast of progress in industry, Australian standards are subject to continuous review and are kept up-to-date by the issue of amendments or new editions as necessary. It is important therefore that standards users ensure that their standards are up-to-date. Full details of all SAA publications will be found in the Annual List of Australian Standards; these details are supplemented by listings in the SAA monthly journal 'The Australian Standard'. Information on the Annual List and 'The Australian Standard' may be obtained from any sales office of the Association, where details are also available of the current status of individual standards. Suggestions for improvements to published standards, addressed to the head office of the Association, are welcomed.

First published 1983

This standard was issued in draft form for comment as DR 81217.

ISBN 0 7262 2739 0

PREFACE

This standard was prepared by the Association's Committee on Coal and Coke under the direction of the Minerals Standards Committee as a further part of AS 1038. It is not technically equivalent to ISO 602, Coal—Determination of Mineral Matter.

The organic material of coal is associated with minerals which have been deposited or formed within the coal. These minerals provide the ash obtained on combustion of the coal; however the mineral matter to ash ratios are quite variable between and within seams. Accordingly, the mineral matter content of coal must be known if coal analyses are to be converted to the dry, mineral-matter-free basis (i.e. organic coal basis) necessary for classification.

Methods of calculating the mineral matter of coal from the percentage ash and other analyses have been specified for British coals in BS 1016, Methods for the Analysis and Testing of Coal and Coke, Part 16—Reporting of Results. These formulas are derived from the mineral compositions and associations found in British coals and are not always appropriate for Australian coals.^{1,2}

ISO 602 specifies a method for the direct determination of mineral matter using an acid demineralization procedure.

The stated repeatability of the ISO method is relatively poor and figures for reproducibility are not given. Inherent in this determination is the necessity to make corrections for ash, insoluble pyrite and absorbed hydrochloric acid; furthermore, the method may yield anomalous results on certain low rank bituminous and lower rank coals.³

The direct determination of mineral matter and water of hydration in Australian coals has been investigated by Brown *et al* who described the following procedures for the determination of mineral matter:

- (a) Low temperature (370°C) oxidation of the coal substance.
- (b) Acid demineralization similar to that specified in ISO 602.

- (c) A combined procedure in which a hydrochloric acid extraction of carbonate, sulphate and phosphate minerals is followed by oxidation at 370°C.

Other methods for the determination of mineral matter are as follows:

- (i) Low temperature (370°C) oxidation, with direct gravimetric determination of combined water.⁴
- (ii) Low temperature (approximately 150°C) oxidation of the coal substance with a radio-frequency excited oxygen plasma.³

An outstanding advantage of the low temperature oxidation procedures over other procedures is that a direct determination of the water of hydration of the coal can be carried out on the separated mineral matter. The mineral matter residues are also suitable for X-ray diffraction examination or chemical analysis.

The committee organized an inter-laboratory test program to obtain information on the repeatability and reproducibility of the methods. The following laboratories participated in the test program to provide the data given in Tables B1 and B2:

Australian Coal Industry Research Laboratories
Ltd
Australian Iron and Steel, Port Kembla
Broken Hill Proprietary Company Ltd, Central
Research Laboratories
Joint Coal Board
SGS Australia Pty Limited
State Electricity Commission of Victoria, Herman
Research Laboratory

1. H.R. Brown, R.A. Durie, and H.N.S. Schafer, *Fuel*, 1959, 38, 295 and *Fuel*, 1960, 39, 50.
2. N.A. Brown, T.G. Callcott, and N.Y. Kirov, 'Notes on Mineral Matter in Australian Coals', Paper A6, Symposium on Australian Fuels and Their Utilization, Newcastle, N.S.W., August 1959. Published by the Australian Membership of the Institute of Fuel.
3. F.W. Frazer and C.B. Belcher, *Fuel*, 1973, 52, 41.
4. N.A. Brown, C.B. Belcher, and T.G. Callcott, *J. Inst. Fuel*, 1965, 38, 198.

© Copyright — STANDARDS ASSOCIATION OF AUSTRALIA 1983

Users of standards are reminded that copyright subsists in all SAA publications. No part of this publication may be reproduced, stored in a retrieval system in any form or transmitted by any means without prior permission in writing of the Standards Association of Australia.

STANDARDS ASSOCIATION OF AUSTRALIA

Australian Standard

METHODS FOR THE ANALYSIS AND TESTING OF COAL AND COKE

PART 22—DIRECT DETERMINATION OF MINERAL MATTER AND WATER OF HYDRATION OF MINERALS IN HARD COAL

1 SCOPE. This standard sets out two methods for the determination of the amounts of mineral matter and water of hydration of minerals in hard coal, viz:

- (a) Air oxidation (370°C).
- (b) Radio-frequency oxygen plasma oxidation.

Both methods are known as low temperature oxidation techniques. The radio-frequency method yields a residue which contains essentially the original unchanged mineral matter of a coal. Predictable alteration of some minerals occurs in the air oxidation process, and appropriate corrections are made.

NOTES:

1. See Appendix A for the applicability of this method to low rank coals.
2. It is advisable to use the radio-frequency (RF) oxygen plasma oxidation method for coals of high ash (and for coals with high gypsum levels), due to significant irreversible loss of water of hydration in the air oxidation method.

2 REFERENCED DOCUMENTS. The following standards are referred to in this standard:

- | | |
|---------|---|
| AS 1038 | Methods for the Analysis and Testing of Coal and Coke
Part 3—Proximate Analysis of Hard Coal
Part 6—Ultimate Analysis of Coal
Part 11—Forms of Sulphur in Coal
Part 16—Reporting of Results |
| AS 1152 | Test Sieves |
| AS 1676 | Methods for the Sampling of Hard Coal |
| AS 2243 | Safety in Laboratories
Part 5—Non-ionizing Radiations |

3 DEFINITIONS. For the purpose of this standard, the following definitions apply:

3.1 Hard coal—mature coal having a gross specific energy of, or in excess of, 27 MJ/kg on a dry ash-free (daf) basis, according to the classification system for Australian hard coals.

3.2 Coal substance—a complex organic material consisting of essentially all the organic carbon, hydrogen, nitrogen, oxygen, and sulphur of coal but excluding moisture, mineral matter and, in the case of lower rank coals, inorganic matter.

The calculation of the composition of this organic matter on a mineral-matter-free basis requires the knowledge of the amount and composition of the mineral matter present in the sample.

3.3 Mineral matter in coal (MM)—the minerals and other inorganic material in, and associated with coal. The mineral component includes water of hydration and the carbon dioxide of mineral carbonates.

3.4 Mineral matter in low rank coal—the mineral matter in low rank coal can be subdivided as follows:

- (a) Minerals—the discrete inorganic material in coal.
- (b) Inorganic matter—elements chemically bound to coal organic matter and water soluble salts in coal.

3.5 Ash (A)—the inorganic residue after the incineration of coal or coke to constant mass under standard conditions. In general it differs in mass and composition from the original mineral matter.

3.6 Low temperature oxidation residue (R)—the product of the low temperature oxidation process after this product has been equilibrated with the laboratory atmosphere. The nature of the product will depend upon the oxidation technique, but is more closely related to the original mineral matter than is ash.

3.7 Moisture (M)—water in coal quantitatively determined by standard methods.

3.7.1 Moisture in air-dried coal (M_{ad})—the moisture retained by the coal sample after it has attained equilibrium with the air to which it is exposed.